AWTA PRODUCT TESTING

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400

TEST REPORT

Test Number:

Issue Date

Print Date

23-004993

19/12/2023

19/12/2023

Client: Advance Flooring Systems Ltd

10 Harbour Ridge Drive Wiri. Auckland 2104

New Zealand

Sample Description Clients Ref : "EverTread"


Interlocking modular entrance matting system

Colour : Silver/Black
End Use : Entrance Matting

Nominal Composition: Aluminium with Polyamide textile inserts

Nominal Mass per Unit Area/Density: 16.55kg/m2

Nominal Thickness: 22mm

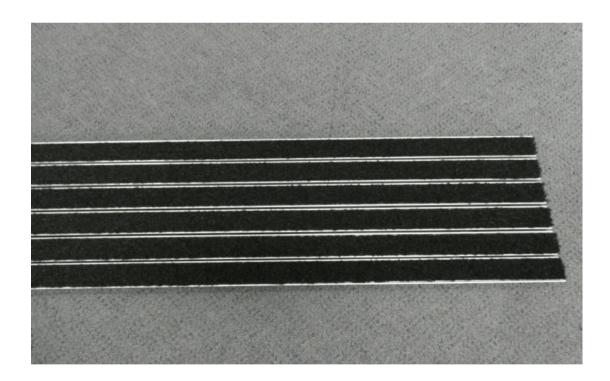

312269 68200 Page 1 of 2

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



APPROVED SIGNATORY



MICHAEL A. JACKSON B.Sc.(Hons)

AWTA PRODUCT TESTING

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400

TEST REPORT

Client: Advance Flooring Systems Ltd

10 Harbour Ridge Drive Wiri. Auckland 2104

New Zealand

Test Number : 23-004993

Issue Date : 19/12/2023 Print Date : 19/12/2023

ISO 9239.1:2010 Part 1

Reaction to Fire Tests for Floorings. Determination of the Burning Behaviour using a Radiant Heat Source

Date of Sample Arrival

05-12-2023

Date Tested

18-12-2023

| CHF Value Length Width | 1 7.9 10.9 | 2 8.2 - | 3 8.4 - | Mean 8.2 | kW/m² kW/m² |
|------------------------------|------------------|---------------|---------------|-------------|----------------|
| Smoke Value Length | 1 41 | 2 45 | 3 32 | Mean 39 | %.min |
| Width | 18 | - | - | - | %.min |

Observation

Melting

Yes

.
The test results relate to the behaviour of the test specimens of a product under the particular

conditions of the test, they are not intended to be sole criterion for assessing the potential fire hazard of the product in use.

Sample was conditioned in accordance with BSEN 13238:2010 at a temperature of 23±2°C and

relative humidity of 50±5% for a minimum of 48 hours prior to testing.

Results in accordance with section 9.4 have not been included in the report. They are available upon request.

Each specimen was clamped to a substrate of 6mm thick fibre reinforced cement board prior to testing.

HF30 not reported as flame out time occurred before 30 minutes.

312269

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved 68200

Page 2 of 2



Accredited for compliance with ISO/IEC 17025 - Testing Accreditation Numbers: 983, 985, and 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

Chris Campbell

ICHAEL A. JACKSON B.Sc. (Hons)

0204/11/06

APPROVED SIGNATORY